

## **DUCTILE FRACTURE IN THE CENTRAL REGION OF CIRCULAR PLATE IN ROTARY FORGING**

SEOGOUI CHOI\* AND HUNG-KUK OH\*\*

\* Metal forming Team, Korea Academy of Industrial Tecnology

\*\* Dept. of Manufacturing and Automation, Ajou University

### **ABSTRACT**

The present investigation is concerned with the application of theory on fracture to the prediction of workability of materials in rotary forging, with special reference to center crack. The validity of the theory on ductile fracture was examined by the experimental data. Then the workability of materials in rotary forging was determined.

### **1. INTRODUCTION**

An accurate determination of the effects of various parameters on metal flow and fracture is a prime requirement for proper design and control of any metalworking process. Without the knowledge of the influence of such variables as friction conditions, materials properties, and process geometry on the process mechanics, it would not be possible to control the change of the metallurgical structure of the deforming material, or to predict and prevent the occurrence of defects. By combining the detailed information on mechanics and the ductile fracture criterion, workability of materials in metalworking processes can be predicted.

The new ductile fracture criterion proposed in the previous paper[1] is developed from the theory of fracture toughness under different mean stress from tensile test. The elongation at fracture decreases linearly with increases of depressive mean stress and the decreasing gradient is determined by the line from yield point to ultimate tensile point in the uniaxial tensile test.

The present investigation has as its object the provision of experimental data for the validity of the proposed new ductile fracture criterion. the validity of the proposed new ductile fracture criterion was examined by the experimental data which are given from upsetting experiments in the rotary forging.

### **2. PROPOSED NEW DUCTILE FRACTURE CRITERION**

Ref.2 shows about the fracture toughness under different mean stress from tensile test that if plastic deformation occurs under different mean stress from tensile test, the elongation, the surface energy per unit area and the fracture toughness are changed because the atomic bonding force reduces or increases with mean stress.

Because the mean stress in uniaxial tensile test is one third of the axial stress, variation of mean stress is equivalent to three times effect in uniaxial stress.

The elongation change caused by mean stress variation is  $(-\Delta \sigma_m / \tan \theta)$  in Fig.1.

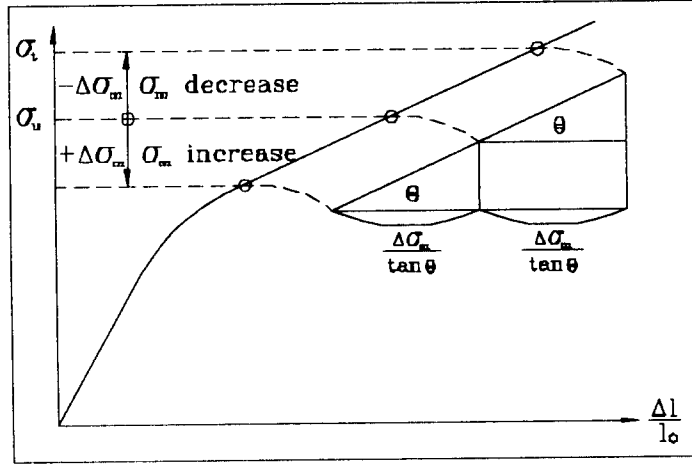


Fig. 1 True stress-elongation curve in uniaxial tensile test with varying mean stress

The changed surface energy per unit area is as follows

$$\gamma_p = \gamma_s \frac{\left\{ \left( \frac{\Delta l}{l_0} \right)_f - \frac{\Delta \sigma_m}{\tan \theta} \right\}}{(\sigma_u - \Delta \sigma_m) / E} \quad (1)$$

where  $\gamma_p$  is total surface energy per unit area,  $\gamma_s$  is brittle elastic surface energy per unit area,  $\Delta \sigma_m$  is mean stress variation, E is Young's modulus of elasticity and  $\sigma_u$  is the ultimate tensile strength.

The proposed new ductile fracture criterion then is as above

$$\left( \frac{\Delta l}{l_0} \right)_{f at \Delta \sigma_m} = \left( \frac{\Delta l}{l_0} \right)_f + \left( \frac{-1}{\tan \theta} \right) \Delta \sigma_m \quad (2)$$

The new criterion means that the material endures elastic and plastic deformation to the time when the mean stress reaches to the maximum sustainable equicohesive bonding stress. As the temperature rises the thermal vibration energy makes the

equicohesive stress decrease. And also at a certain temperature and stress state the cohesive force decreases as the time elapses.

Therefore temperature rise, time elapse and depressive mean stress's increase reduce the equicohesive bonding stress in the material. The material fractures at the time when the equicohesive bonding stress can not sustain external mean stress. The plastic deformation also reduces the equicohesive bonding stress by damaging its microstructure.

### 3. DUCTILE FRACTURE IN THE CENTRAL REGION OF BILLET IN ROTARY FORGING

The mechanics and mechanism of ductile fracture in metals are significant for both engineers and metallurgists in designing against plastic collapse and fracture of structures and workpieces. The avoidance of ductile fracture is of importance in metal forming processes, such as design of the process and die in forging, extrusion and drawing.

Rotary forging is an incremental deformation process in which the deformation is the continuous local deformation instead of the deformation as a whole in conventional forging(Fig.2), so the process is particularly attractive for producing thin flanges which normally result in appreciable frictional restraint to spread. Nevertheless, while thin circular plates are made by rotary forging, ductile fracture in the central region of workpieces shown in Fig.3 will occurs under any given conditions[3,4].

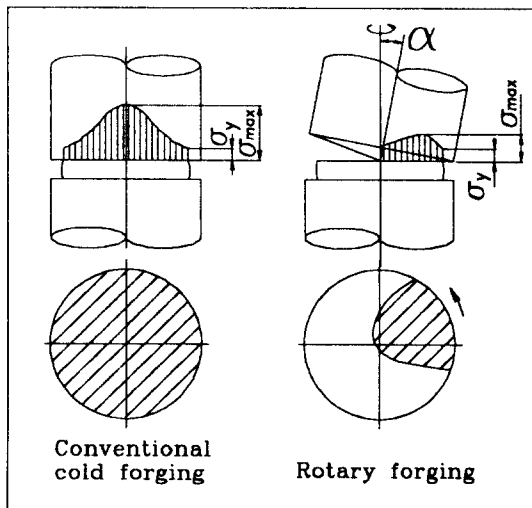


Fig.2. Principle of rotary forging.

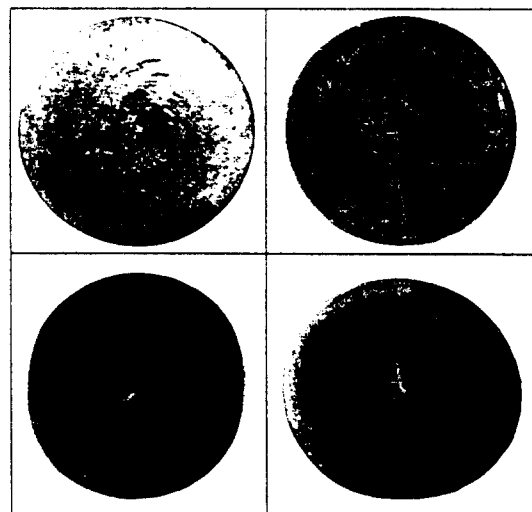


Fig.3. Samples fractured at center

The present investigation is concerned with the application of theory on fracture to

the prediction of workability of materials in rotary forging, with special reference to center crack. Experiments on rotary forging were conducted for examining the validity of the new ductile fracture theory.

### A. Experimental data

Experiments has been conducted to observe central crack in rotary forging for aluminum alloy 6061 and carbon steel (0.45%C) at room temperature. The experimental conditions were as follows:

1. Tensile test : Testing was performed at room temperature on an Instron testing machine at a nominal strain rate of 0.03mm/mm/min. Measurements of extension were performed continuously until fracture with an extensometer exhibiting a strain sensitivity of at least 0.0005mm/mm.

Table 1 Dimensions and Stress-strain relationship of workpiece

	Height H <sub>0</sub> /mm	Diameter D <sub>0</sub> /mm	$\bar{\sigma} = A\bar{\epsilon}^n$ (Kg / mm <sup>2</sup> )
Steel (0.45%C)	10.0	25.0	$\bar{\sigma} = 130(\bar{\epsilon})^{0.25}$
	15.0	25.0	
Aluminun (Al6061)	10.0	25.0	$\bar{\sigma} = 68.1(\bar{\epsilon})^{0.21}$
	15.0	25.0	

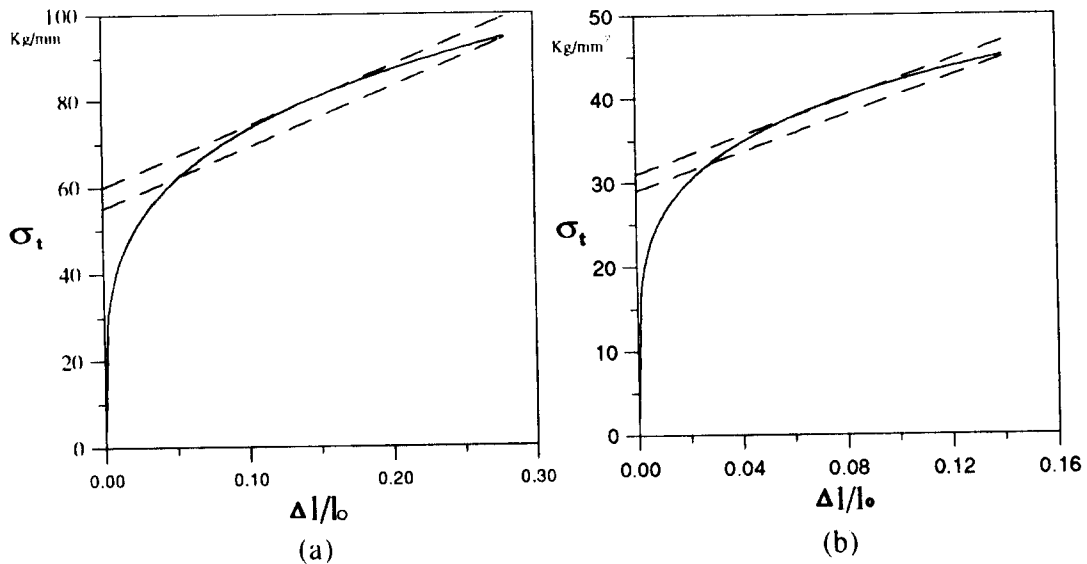


Fig. 4 True stress-elongation curve in uniaxial tensile test (a) steel (0.45%C) (b) aluminum(A6061)

2. Upsetting in rotary forging : Experiments were conducted in the rotary forging press which has been designed and constructed in our laboratory[5]. The forming load is supported by the hemispherical bearing. Pressure-raised oil is supplied for the lubrication of the bearing surface. To reduce required load a slightly larger angle of Upper die of 3 degrees is used. Therefore experiments have been carried out only in case of 3 degrees. The materials were prepared shown in table 1.

3. Results : Tension test results are shown in table 1 and Fig. 4 and upsetting experiment results are shown in Fig. 5.

## B. Computation and results

Using 3-d slab method and plastic hinge model, the stress components in the central part of workpiece were analyzed for the material A6061 and carbon steel(0.45%C). The detailed mechanics were presented in the previous paper[6]. Therefore the mean stress in the central part of workpiece can be obtained from the above analysis.

From the proposed ductile fracture criterion and the tension tests, we can derived the following relationship

$$\text{steel (0.45\%C)} : \left( \frac{\Delta l}{l_o} \right)_{f \text{ at } \Delta \sigma_m} = \left( \frac{\Delta l}{l_o} \right)_f + \left( \frac{-1}{\tan \theta} \right) \Delta \sigma_m = 0.28 + \left( \frac{-1}{140} \right) \Delta \sigma_m \quad (3)$$

$$\text{Al (A6061)} : \left( \frac{\Delta l}{l_o} \right)_{f \text{ at } \Delta \sigma_m} = \left( \frac{\Delta l}{l_o} \right)_f + \left( \frac{-1}{\tan \theta} \right) \Delta \sigma_m = 0.14 + \left( \frac{-1}{113} \right) \Delta \sigma_m \quad (4)$$

From the above eqns and stress analysis, the following relationship on center cracks in the central region can be obtained in rotary forging.

$$\text{steel (0.45\%C)} : \frac{f}{h} = 0.0085 \left( \frac{R}{h} \right)^{1.6} \quad , \alpha = 3^\circ \quad (5)$$

$$\text{Al (A6061)} : \frac{f}{h} = 0.011 \left( \frac{R}{h} \right)^{1.588} \quad , \alpha = 3^\circ \quad (6)$$

where f is feeding rate of rocking die per revolution, h is current height of workpiece, R is current radius of workpiece and  $\alpha$  is inclination angle of upper die.

The meaning of the eqns(5)and (6) is that center crack occurs when  $(f/h) < 0.0085(R/h)^{1.6}$  in case of steel(0.45%C) and  $(f/h) < 0.011(R/h)^{1.588}$  in case of Al(A6061), that is, the right and lower part of the curve is the center crack region(Fig. 5).

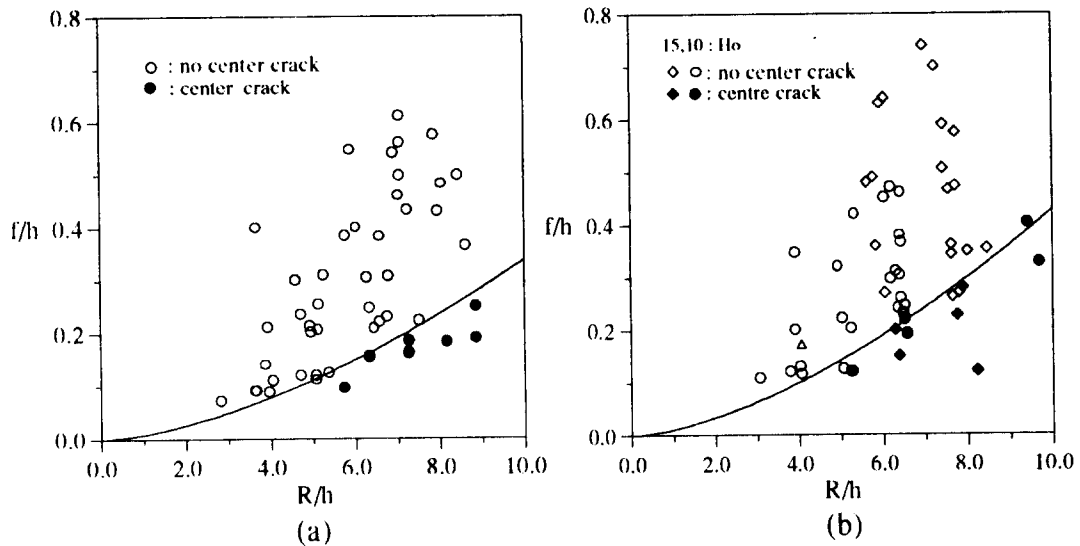


Fig.5. Comparison between theoretical criterion on center crack and experimental center crack (a) steel(0.45%C) (b) aluminum(A6061)

As the result of theoretical analysis about center crack in rotary forging, the following facts are observed.

- 1)The height that center crack begins( $h$ ) does not depend on the original height of workpiece and the rotational speed and the materials.
- 2)The height that center crack begins( $h$ ) increases with the decreasing of the feeding rate of rocking die per revolution( $f$ ) and the radius of workpiece.

In Fig.5, the calculated criterion on center crack is compared with the experimental data. The calculated results agree fairly well with the experimental ones. It is found that there is good agreement between the theoretical criterion of the center crack and the experimental results. Therefore the ductile fracture limit in the central region of circular plate in rotary forging can be determined by eqn. 2.

Although conclusive validity of the present ductile fracture theory in rotary forging awaits more extensive and systematic experimental investigations, as well as theoretical calculation, the method of computation is available and the approach has been cleared toward complete understanding of ductile fracture in metalworking processes.

#### 4. CONCLUSION

1. From the proposed new ductile fracture criterion, the theoretical prediction on center crack in rotary forging is made. The calculated results agree fairly well with the experimental ones.

2. As the result of theoretical analysis on center crack in rotary forging, we can understand the mechanics of center crack in rotary forging.
3. Therefore the ductile fracture limit in rotary forging can be determined by eqn.(2).
4. But to verify certainly the validity of the new ductile fracture criterion, the more extensive and systematic experimental investigations have to make steady progress.

## REFERENCES

1. H.K. Oh, Determination of ductile fracture(ductility) at any stress state by uniaxial tensile test, J. Mat. Pro. Tech., V.53, N.3-4, (1995), pp582-587
2. H.K. Oh, Determination of fracture toughness by uniaxial tensile test, J. Mat. Pro. Tech., In Press.
3. D. Zhou, S. Yuan, Z.R.Wang and Z. Xiao, Defects caused in forming process of rotary forged parts and their preventive method, J. Mat. Pro. Tech., 32, (1992), pp471-479.
4. Q. Lu, Z. Liu and J. Wei, Criterion of center thinning in rotary forging of circular plate, 2nd. Int. Conf. Romp, (1982), pp137-148.
5. S. Choi, K.H. Na and et. al., The development of a rotary forging machine and its practical applications, Proceedings of KSTP '92 Autumn Annual Meeting, Oct. (1992), pp107-113.
6. H.K. Oh and S. Choi, A study on center thinning in rotary forging of circular plate, J. Mat. Pro. Tech., Submission in July, 1995.