

Properties of $\text{YBa}_2\text{Cu}_3\text{O}_x$ with PbO and BaPbO_3 additives

Fan Zhanguo*, Soh Daewha**, Cho Yongjoon**

*Northeastern University, China, **Myongji University, Korea
fanzg@mail.sy.ln.cn

Abstract— The melting temperature and critical temperature (Tc) of $\text{YBa}_2\text{Cu}_3\text{O}_x$ with different content impurities of PbO and BaPbO_3 were studied. When the PbO was used as addition in $\text{YBa}_2\text{Cu}_3\text{O}_x$, although the melting point could be reduced, the superconductivity (the transition wide, ΔT_c) became poor. From the XRD pattern of the sintered mixture of $\text{YBa}_2\text{Cu}_3\text{O}_x$ and PbO it was known that there is a reaction between $\text{YBa}_2\text{Cu}_3\text{O}_x$ and PbO, and the product is BaPbO_3 . In the process of the reaction the superconducting phase of $\text{YBa}_2\text{Cu}_3\text{O}_x$ was decreased and in the sample BaPbO_3 became the main phase. Therefore the superconductivity was reduced. BaPbO_3 was chosen as the impurity for the comparative study. The single phase BaPbO_3 was synthesized by the simple way from both mixtures of BaCO_3 and PbO, BaCO_3 and PbO_2 . Different contents of BaPbO_3 (10%, 20%, 30%) were added in the $\text{YBa}_2\text{Cu}_3\text{O}_x$. By the phase analysis in the XRD patterns it was proved that there were not reactions between $\text{YBa}_2\text{Cu}_3\text{O}_x$ and BaPbO_3 . When BaPbO_3 was used as impurity in $\text{YBa}_2\text{Cu}_3\text{O}_x$ the superconductivity was much better than PbO as impurity in $\text{YBa}_2\text{Cu}_3\text{O}_x$. But the melting point of $\text{YBa}_2\text{Cu}_3\text{O}_x$ with BaPbO_3 could not be found when the temperature was lower than 1000 °C in the DTA measurement.

I. INTRODUCTION

BiPbSrCaCuO system is well known developed in making superconducting tape by powder in tube method nowadays in the world, but its critical current decreases very fast with the increasing magnetic field, that is the main drawback to be overcome difficultly. $\text{YBa}_2\text{Cu}_3\text{O}_x$ superconductor has good superconductivities under higher magnetic field, but Powder In Tube method (PIT) can not be used for $\text{YBa}_2\text{Cu}_3\text{O}_x$ superconductor due to that its melting point is about 50 °C higher than that of silver. The scientists are trying to utilize the methods for preparation of $\text{YBa}_2\text{Cu}_3\text{O}_x$ superconducting films to fabricate wires or tapes [1, 2, 3, 4, 5,].

Almost all the equipments are operated in vacuum and the long wire preparation is very difficult. If the melting temperature of $\text{YBa}_2\text{Cu}_3\text{O}_x$ could be reduced below the melting point of Ag the PIT technique for Bi system wires can be used for the preparation of $\text{YBa}_2\text{Cu}_3\text{O}_x$ wire. One way to reduce the melting temperature is to add one low melting point substance into $\text{YBa}_2\text{Cu}_3\text{O}_x$ matrix according to the thermodynamic principle. The substance must have following properties: (1) It is stable in the $\text{YBa}_2\text{Cu}_3\text{O}_x$ matrix, it does not react with $\text{YBa}_2\text{Cu}_3\text{O}_x$; (2) It can not reduce the superconductivities of $\text{YBa}_2\text{Cu}_3\text{O}_x$ when it is added into $\text{YBa}_2\text{Cu}_3\text{O}_x$. In the experiment different contents of PbO and BaPbO_3 were added in the $\text{YBa}_2\text{Cu}_3\text{O}_x$ matrix, the chemical reactions between the additives and $\text{YBa}_2\text{Cu}_3\text{O}_x$ as well as the transition temperatures were studied respectively.

II. EXPERIMENT

2-1 Preparation of samples of $\text{YBa}_2\text{Cu}_3\text{O}_x$ with additions and the property measurement



$\text{YBa}_2\text{Cu}_3\text{O}_x$ powder was synthesized by the sol-gel method [x], which was single phase, 90 K zero resistance and 0.2-1.0 μm of particle size.

In the first group samples 5 wt%, 10 wt%, 15 wt% of PbO were added in $\text{YBa}_2\text{Cu}_3\text{O}_x$. In the second group samples 10wt%, 20wt%, and 30wt% of BaPbO_3 were added in $\text{YBa}_2\text{Cu}_3\text{O}_x$. The mixture pellets were heated to 800 °C for 10 hours. The samples were oxygenated at 400 °C for 10 hours after sintering. The superconductive transition temperature was measured with standard four lines method, and the phase composition was examined with X-ray diffraction (XRD).

2-2 Sintering of BaPbO_3

The synthesis of BaPbO_3 has been presented by different ways [6, 7].

In the experiment BaPbO_3 was synthesized from the mixture of BaCO_3 and PbO or PbO_2 . The reactions in the synthesis processing respectively are:



The mixture samples were sintered at 800 °C in air for 10 hours. The phase composition of the product was examined by XRD. The XRD patterns of samples sintered from equation (1) and (2) are shown in figure 1. Comparing the XRD data with the standard one [8], it is

proved that the products are single phase BaPbO₃, which could be sintered using either PbO or PbO₂ in air.

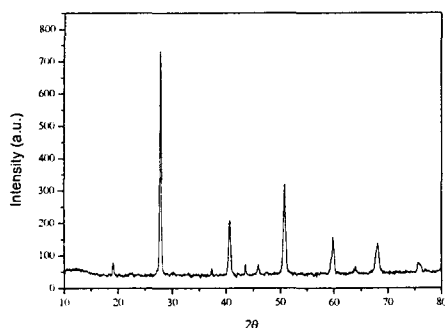


Fig. 1. XRD pattern of BaPbO₃ sintered from BaCO₃ and PbO or PbO₂

III. RESULTS AND DISCUSSION

3-1. The effects of PbO on the melting temperature and critical temperatures of YBa₂Cu₃O_x

The relation of YBa₂Cu₃O_x and the PbO contents are shown in figure 2.

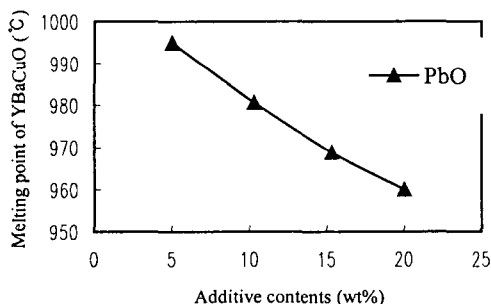


Fig. 2. The melting points of YBa₂Cu₃O_y with different PbO contents

The melting temperature of YBa₂Cu₃O_x is decreased with the increasing PbO contents. When the PbO content reaches 20wt% the melting temperature reduces to about 960°C. From the results the melting temperature was reduced remarkably with the increasing PbO contents. After the measurements of critical temperature (T_c) of the PbO doped YBa₂Cu₃O_x and the transition wide (ΔT_c) are shown as in table 1.

Although the PbO doped YBa₂Cu₃O_x samples are 90 K zero resistance superconductors, their transition wide are about 11 K, for comparison, ΔT_c of pure YBa₂Cu₃O_x sample is only 3 K. It is reasonable to think that there is a reaction between PbO and YBa₂Cu₃O_x and PbO is not a independent phase in YBa₂Cu₃O_x matrix. The reaction and the result may have effect on the superconductivities of YBa₂Cu₃O_x.

Table 1 PbO content and its effect on the critical temperature

| Sample | PbO (wt %) | T _{c, onset} , K | ΔT _c , K | T _{c0} , K |
|--------|------------|---------------------------|---------------------|---------------------|
| 1 | 0 | 92.0 | 3.0 | 89 |
| 2 | 5 | 90.3 | 11.2 | 81.1 |
| 3 | 10 | 92.6 | 11.5 | 81.1 |
| 4 | 15 | 91.0 | 11.2 | 80.8 |
| 5 | 20 | 88.2 | 11.6 | |

3-2 The chemical reactions between PbO and YBa₂Cu₃O_x

A sample with components of YBa₂Cu₃O_x (70%), PbO (20%), Ag (10%) was heated at 850°C for 5 hours. The sample was examined by X-ray diffraction (XRD). The XRD pattern is shown in figure 3. In the XRD pattern the main phase is BaPbO₃, and other two phases are YBa₂Cu₃O_x and Ag. The PbO phase disappeared and YBa₂Cu₃O_x phase reduced obviously.


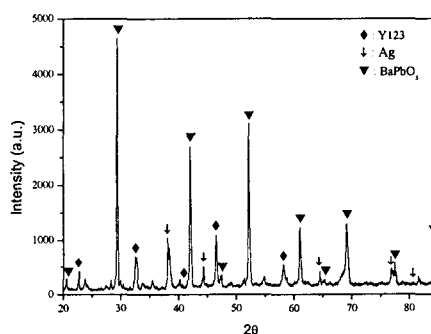


Fig. 3. XRD of Sintered mixture of YBa₂Cu₃O_x, PbO and Ag

It can be deduced that there is a reaction between YBa₂Cu₃O_x and PbO, the product of the reaction is BaPbO₃, that is:



The mole ratio should be 42.4 mol% of PbO and 57.6 mol% of YBa₂Cu₃O_{6.5}, if the addition of PbO is 20 wt% in YBa₂Cu₃O_{6.5}. According to reaction (1), 21.2 mol% YBa₂Cu₃O_{6.5} would be consumed, and remained YBa₂Cu₃O_{6.5} is 57.6-21.2=36.4mol%, which has the mole ratio of 23.8 mol% in products after sintering. That small superconductive phase (23.8 mol%) may be the reason of large transition wide (ΔT_c).

The chemical reaction is an oxidized process. If the reaction was controlled in low oxygen partial pressure or in inert gas the oxidation process may be suppressed.

3-3. Study of properties of YBa₂Cu₃O_x added with BaPbO₃

BaPbO₃ was studied as additive in YBa₂Cu₃O_x by several authors [10, 11], and it is a promising intergranular material for synthesis of YBa₂Cu₃O_x composites.

In the experiment 10%, 20% and 30% of BaPbO₃ were added in the YBa₂Cu₃O_x matrix. The XRD patterns of YBa₂Cu₃O_x with different BaPbO₃ contents are shown in figure 4.

In each XRD pattern in figure 4 there are not any other impurity phases except the original two phases, YBa₂Cu₃O_x and BaPbO₃, and the diffraction intensities of BaPbO₃ increase proportionally with increasing its content in YBa₂Cu₃O_x matrix. It can be concluded that there are not any chemical reactions between YBa₂Cu₃O_x and BaPbO₃.

The critical temperature of above 3 samples was measured by 4 probe method. The results are shown as in table 2.

Table 2 Superconductivity of YBa₂Cu₃O_x with BaPbO₃

| Sample | T _{c,onset} , K | ΔT _c , K | T _{c0} , K |
|---------------|--------------------------|---------------------|---------------------|
| Y123 | 91.2 | 0.75 | 90.45 |
| Y123 + 10%BPO | 91.2 | 6.0 | 85.2 |
| Y123 + 20%BPO | 91.9 | 3.7 | 88.2 |
| Y123 + 30%BPO | 90.5 | 6.7 | 83.8 |

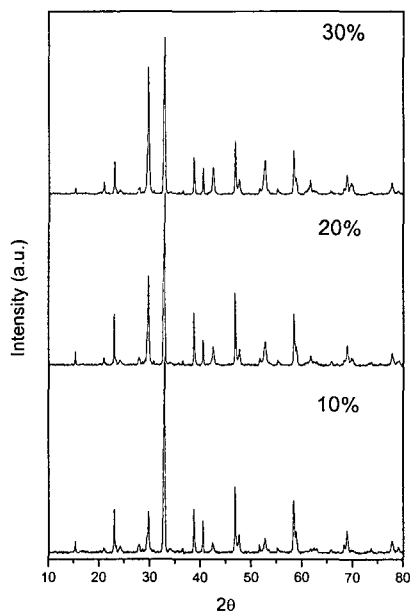


Fig. 4. XRD patterns of YBa₂Cu₃O_x with 10%, 20%, and 30% of BaPbO₃

From table 2 it can be seen that ΔT_c and T_{c0} of YBa₂Cu₃O_x with BaPbO₃ were improved compared with that of YBa₂Cu₃O_x with PbO in table 1. Unfortunately, the melting temperature of YBa₂Cu₃O_x doped with BaPbO₃ could not be found when the temperature was lower than 1000 °C in the DTA measurement.

IV. CONCLUSIONS

When the PbO was used as addition for reducing the melting point of YBa₂Cu₃O_x, although the melting point could be reduced, the superconductivity (the transition wide, ΔT_c) became pure. There is a reaction between YBa₂Cu₃O_x and PbO, and the product is BaPbO₃, which was studied from XRD phase analysis. In the process of the reaction the superconducting phase of YBa₂Cu₃O_x was decreased and in the sample BaPbO₃ became the main phase. Therefore the superconductivity was reduced. The single phase BaPbO₃ was synthesized by the simple way from both mixtures of BaCO₃ and PbO, BaCO₃ and PbO₂. Different contents of BaPbO₃ (10%, 20%, 30%) were added in the YBa₂Cu₃O_x. There are not reactions between YBa₂Cu₃O_x and BaPbO₃. When BaPbO₃ was used as impurity in YBa₂Cu₃O_x the superconductivity was much better than PbO as impurity in YBa₂Cu₃O_x. But the melting point of YBa₂Cu₃O_x with BaPbO₃ could not be found when the temperature was lower than 1000 °C in the DTA measurement.

REFERENCES

- [1] K. Hasegawa, K. Fujimo, H. Mukai, et al, Appl. Supercond. 4 (1998) 487.
- [2] M. Fukutomi, S. Aoki, et al, Physica C 219 (1994) 333.
- [3] A. Goyal, D.P. Norton, et al, J. Mater. Res. 12 (1997) 2924.
- [4] K. Onabe, H. Akata, in: T. Yamashita, (Eds.), Adv. Superconductivity VII, Springer, Tokyo, 2000, p.598.
- [5] H. Yoshino, M. Yamazaki, in: T. Yamashita (Eds.), Adv. Superconductivity VII, Springer, Tokyo, 2000, p.583.
- [6] Zhang Shengli, Wang Shimin, Chen Zuxing, et al, "Preparation of BaPbO₃ conductive powders by sol-gel process", Journal of Hubei University (Natural Science Edition), Vol.23, No.4(2001) 335-337 (in Chinese)
- [7] Liu Xinyu, Zhan meiyuan, Zhou Ming, "Solid Phase Preparation of BaPbO₃ Conductive Ceramic Powder", Rare Metals and Hard alloys, vol.138(1999) 11-14 (in Chinese)
- [8] 1995 JCPDS-International Centre for Diffraction Data, 12-0664, BaPbO₃
- [9] A. G. Mamalis, S. G. Ovchinnikov, M. I. Petrov, et al, "Composite materials on high-T_c superconductors and BaPbO₃, Ag basis", Physica C, Vol. 364-365(2001)174-177.
- [10] Ji-Yeon Kim, Su-Young Lee, In-Sang Yang, et al, "Raman and infrared spectroscopy of YBa₂Cu₃O_x - BaPbO₃ composites", Physica C, Vol. 308(1998) 60-66.