

- 1966, 88, 5121.
- Collman, J. P. *Acc. Chem. Res.* 1975, 8, 342.
  - Darensbourg, M. Y.; Darensbourg, D. J.; Drew, D. A.; Burns, D. J. *J. Am. Chem. Soc.* 1976, 98, 3127.
  - Moro, A.; Foa, M.; Cassar, L. J. *Organomet. Chem.* 1980, 212, c68.
  - (a) Darensbourg, M. Y.; Jimenez, P.; Sackett, J. R.; Hankel, J. M.; Kump, R. L. *J. Am. Chem. Soc.* 1982, 104, 1521; (b) Darensbourg, M. Y.; Jimenez, P.; Sackett, J. R. *J. Organomet. Chem.* 1980, 202, c68.
  - Winston, P. L.; Bergman, R. G. *J. Am. Chem. Soc.* 1979, 101, 2055.
  - Darensbourg, M. Y. *Progress in Inorganic Chemistry*; John Wiley & Sons, Inc.: New York, U. S. A., 1985; Vol. 33, p 222.
  - Park, Y. K.; Han, I. S.; Huh, T. S. *Bull. Kor. Chem. Soc.* 1990, 11, 221.
  - Park, Y. K.; Kim, S. J.; Kim, J. H.; Han, I. S.; Lee, C. H.; Choi, H. S. *J. Organomet. Chem.* 1991, 408, 193.
  - Anders, U.; Graham, W. A. *J. Am. Chem. Soc.* 1967, 89, 539.
  - Arndt, L. W. Dissertation, Texas A & M Univ. 1986.
  - Ruff, J. K. *Inorg. Chem.* 1968, 7, 1818.
  - Closson, R. D.; Kozikowski, J.; Coffield, T. H. *J. Org. Chem.* 1966, 22, 598.
  - Hayter, R. G. *J. Am. Chem. Soc.* 1966, 88, 4376.

## Study of Nonstoichiometry and Physical Properties of the $\text{Ca}_x\text{Eu}_{1-x}\text{FeO}_{3-y}$ System

Kwon Sun Roh, Kwang Sun Ryu, Kwang Hyun Ryu, and Chul Hyun Yo

Department of Chemistry, Yonsei University, Seoul 120-749, Korea

Received January 27, 1994

A series of samples of the  $\text{Ca}_x\text{Eu}_{1-x}\text{FeO}_{3-y}$  ( $x=0.00, 0.25, 0.50, 0.75,$  and  $1.00$ ) system has been prepared at  $1,250^\circ\text{C}$  under an atmospheric air pressure. X-ray diffraction analysis of the solid solution assigns the structure of the compositions of  $x=0.00, 0.25, 0.50,$  and  $0.75$  to the orthoferrite-type orthorhombic system, and that of  $x=1.00$  to the brownmillerite-type orthorhombic one. The mole ratios of  $\text{Fe}^{4+}$  ion in the solid solutions or  $\tau$  values were determined by the Mohr's salt analysis and nonstoichiometric chemical formulas of the system were formulated from  $x, \tau,$  and  $y$  values. From the result of the Mössbauer spectroscopy, the coordination and magnetic property of the iron ion are discussed. The electrical conductivities are measured as a function of temperature. The activation energy is minimum at the composition of  $x=0.25$ . The conduction mechanism can be explained by the hopping of electrons between the mixed valences of  $\text{Fe}^{3+}$  and  $\text{Fe}^{4+}$  ions.

### Introduction

Perovskite-type compounds,<sup>1-7</sup>  $\text{ABO}_3$ , have been extensively studied because of their unique and applicable properties due to the mixed valence state of B ion and oxygen vacancy. The properties can be controlled by the substitution of lower valence metals such as  $\text{Ca}^{2+}, \text{Sr}^{2+},$  and  $\text{Ba}^{2+}$  in place of higher one,  $\text{Ln}^{3+}$ , as well as the heating temperature and oxygen pressure maintained during the synthesis.

The orthoferrites<sup>8</sup> have the formula of  $\text{RFeO}_3$  where R is rare earth metals. The ferrite has the distorted perovskite structure in which the iron environment retains essentially octahedral but an octahedral chain along a  $c$ -axis has the form of zigzagging. The degree of zigzagging is determined to a large extent by the size of R ion. The larger the R ion, the more the chain stretches, the degree of zigzagging decreases. The substitution of larger alkaline earth metal in place of rare earth metal accelerates the phenomenon. The compositions of  $x=0.50$  and  $0.25$  in the  $\text{Sr}_x\text{La}_{1-x}\text{FeO}_{3-y}$  and  $\text{Ba}_x\text{La}_{1-x}\text{FeO}_{3-y}$  systems<sup>6,9</sup> have the ideal cubic perovskite structure in which Fe-O-Fe angle is  $180^\circ$ . In these systems, the valence state of Fe ion changes partly from

the trivalent to the tetravalent state with increasing  $\text{Sr}^{2+}$  or  $\text{Ba}^{2+}$  ion content and the electrical conductivity increases. The magnetic ordering temperature decreases with increasing  $x$  value, which is explained by the superexchange model.<sup>10</sup>

In the study of defect model for perovskite oxides, Roosmalen *et al.*<sup>11</sup> have suggested that in the  $\text{SrMnO}_{3-y}$ , the  $\text{Mn}^{3+}$  ions are coordinated trigonal bipyramidally and octahedrally, while the structure for  $\text{SrFeO}_{3-y}$  consists of tetragonally and octahedrally coordinated iron ions. Grenier *et al.*<sup>12</sup> have investigated the Mössbauer resonance effect on the  $\text{Ca}_2\text{La}_{1-2y}\text{FeO}_{3-y}$  system in which the ratios of six and four coordinated iron ions increase with  $y$  value, while the variation of Néel temperature is not significant on the contrary, in  $\text{Sr}_x\text{La}_{1-x}\text{FeO}_{3-y}$  and  $\text{Ba}_x\text{La}_{1-x}\text{FeO}_{3-y}$  systems.

The  $\text{CaFeO}_3$ <sup>13,14</sup> prepared only under higher oxygen partial pressure, has the crystal structure distorted slightly from cubic system and the charge disproportionation of  $\text{Fe}^{4+}$  ion into  $\text{Fe}^{3+}$  and  $\text{Fe}^{5+}$  ions occurs at the liquid helium temperature. The  $\text{CaFeO}_{2.5}$  system<sup>15,16</sup>, however, has the brownmillerite-type orthorhombic structure in which the oxygen vacancy ordering along  $[101]$  strings occurs in every other (010) plane and a slight shift of the iron atoms in these planes

leads to a structure with alternating sheets of (FeO<sub>6</sub>) octahedra and of (FeO<sub>4</sub>) tetrahedra.

In the present study, the solid solutions of the Ca<sub>x</sub>Eu<sub>1-x</sub>FeO<sub>3-y</sub> ( $x=0.00, 0.25, 0.50, 0.75,$  and  $1.00$ ) system have been prepared and their structures are analyzed by X-ray diffraction. The amount of Fe<sup>4+</sup> ion or the mixed valence state between Fe<sup>3+</sup> and Fe<sup>4+</sup> ions is determined by Mohr's salt titration. The nonstoichiometric chemical formula for the Ca<sub>x</sub>Eu<sub>1-x</sub>Fe<sup>3+</sup><sub>1-τ</sub>Fe<sup>4+</sup><sub>τ</sub>O<sub>3-y</sub> system is determined. The Mössbauer resonance effect and electrical conductivity will be discussed with the nonstoichiometric compositions.

## Experimental

Solid solutions for the compositions of  $x=0.00, 0.25, 0.50, 0.75,$  and  $1.00$  in the Ca<sub>x</sub>Eu<sub>1-x</sub>FeO<sub>3-y</sub> system have been prepared as follows. The starting materials such as Eu<sub>2</sub>O<sub>3</sub>, CaCO<sub>3</sub>, and Fe(NO<sub>3</sub>)<sub>3</sub>·9H<sub>2</sub>O were weighed and dissolved in the dilute nitric acid. The solution was evaporated over a burner flame and then the nitrates were decomposed at 800 °C for 4 hours. After being ground and mixed, the mixtures were heated at 1,250°C under an atmospheric air pressure for 36 hours. The grinding and heating processes were repeated several times in order to produce homogeneous solid solution.

The solid solutions are identified by the powder X-ray diffraction analysis with a PHILIPS pw 1710 diffractometer using monochromatized CuKα ( $\lambda=1.5406$  Å) radiation. Lattice parameters, reduced lattice volume of the unit cell, and crystal system for the solid solutions were determined reasonably.

The chemical analysis was carried out to determine the oxidation state of the iron ions by dissolving the samples in 0.1 N solution of Mohr's salt in the presence of HCl and titration with K<sub>2</sub>Cr<sub>2</sub>O<sub>7</sub> solution. The results obtained were reproducible and self-consistent. Oxygen vacancy and nonstoichiometric chemical formulas for the system were also determined.

The Mössbauer spectra were recorded at room temperature using a spectrometer consisted of a 308-channel pulse-height analyzer and a source of <sup>57</sup>Co/Rh with 14.4 KeV  $\gamma$ -radiation. Isomer shift, quadrupole splitting, and hyperfine field were determined relative to the spectrum of  $\alpha$ -Fe.


Electrical conductivity measurements were carried out on the pressed and sintered pellets using four probe *d.c.* technique in the temperature range of 173 to 873 K under ambient atmosphere. Electrical conductivities were calculated by Laplumbe's equation.

## Results and Discussion

Solid solutions with the compositions of  $x=0.00, 0.25, 0.50, 0.75,$  and  $1.00$  in the Ca<sub>x</sub>Eu<sub>1-x</sub>FeO<sub>3-y</sub> system have been prepared at 1250°C under an atmospheric air pressure. From the result of the powder X-ray diffraction analysis for all the compositions the patterns show two crystallographically distinct phases. The compositions of  $x=0.00, 0.25, 0.50,$  and  $0.75$  present characteristic patterns of the orthoferrite-type orthorhombic perovskite, while the composition of  $x=1.00$  represents the brownmillerite one without any other phase evidence.

**Table 1.** Lattice Parameters, Reduced Lattice Volume, and Crystal System for the Ca<sub>x</sub>Eu<sub>1-x</sub>FeO<sub>3-y</sub> System

$x$ value	Lattice parameters (Å)			Reduced lattice volume (Å <sup>3</sup> )	Crystal system
	$a$	$b$	$c$		
0.00	5.338	5.564	7.648	227.2	orthorhombic
0.25	5.375	5.585	7.666	230.1	orthorhombic
0.50	5.389	5.594	7.669	231.2	orthorhombic
0.75	5.410	5.598	7.652	231.7	orthorhombic
1.00	5.432	14.76	5.607	224.7	orthorhombic

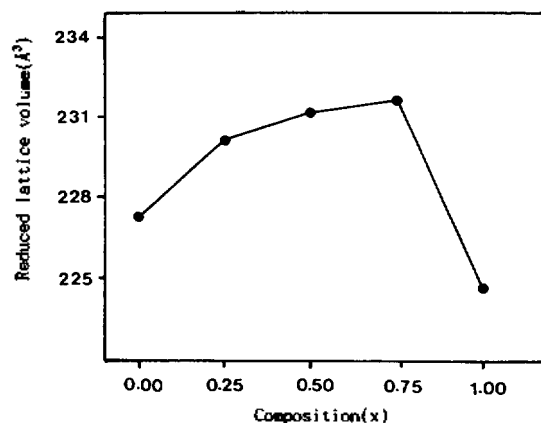




**Figure 1.** Plot of reduced lattice volume vs.  $x$  value for the Ca<sub>x</sub>Eu<sub>1-x</sub>FeO<sub>3-y</sub> system.

Lattice parameters, reduced lattice volume of the unit cell, and crystal system for the corresponding compositions are listed in Table 1. The unit cell volume of ABO<sub>3</sub> system is affected by three factors such as the ionic radius of the substituted ion in the A-site, the oxygen vacancy, and the mixed valence state of the B-site. As shown in Figure 1, the reduced cell volume increases with the  $x$  value in the range of  $0.00 \leq x \leq 0.75$ . However, the volume decreases at the composition of  $x=1.00$  where phase transition occurs. Considering the similar radii of the A-site ions and slight formation of the mixed valence state of the B-site, the oxygen vacancy results in the decreasing covalency between the iron ions, so that the effect is predominant in our system.

The mole ratio of Fe<sup>4+</sup> ion or  $\tau$  value, the amount of oxygen vacancy or  $y$  value, and the nonstoichiometric chemical formula corresponding to each composition are listed in Table 2. The composition of  $x=0.00$  or EuFeO<sub>3.00</sub> is a stoichiometric compound and the others are all nonstoichiometric compounds. The composition of  $x=0.25$  has the maximum  $\tau$  value as shown in Figure 2. However, the  $\tau$  value decreases steadily with increasing  $x$  value in the range of  $0.25 \leq x \leq 1.00$  in which the formation of oxygen vacancies might be easier than the formation of Fe<sup>4+</sup> ion. Thus the  $y$  value increases with the  $x$  value and the ordering of the vacancies decreases the lattice energy. According to the X-ray diffraction analysis, it was found that oxygen vacancies in the compositions of the range of  $0.25 \leq x \leq 0.75$  are randomly distributed in the orthoferrite-type ( $2^b a_c \times 2^b a_c \times 2a_c$ ) unit cell. However, the oxygen vacancy ordering occurs in the composition of  $x=1.00$

**Table 2.**  $x$ ,  $\tau$ ,  $y$  Values, and Nonstoichiometric Chemical Formula for the  $\text{Ca}_x\text{Eu}_{1-x}\text{FeO}_{3-y}$  System

$x$	$\tau$	$y$	Chemical Formula
0.00	0.00	0.00	$\text{EuFe(II)O}_{3.00}$
0.25	0.09	0.08	$\text{Ca}_{0.25}\text{Eu}_{0.75}\text{Fe(III)}_{0.91}\text{Fe(IV)}_{0.09}\text{O}_{2.92}$
0.50	0.05	0.23	$\text{Ca}_{0.50}\text{Eu}_{0.50}\text{Fe(III)}_{0.96}\text{Fe(IV)}_{0.05}\text{O}_{2.77}$
0.75	0.04	0.36	$\text{Ca}_{0.75}\text{Eu}_{0.25}\text{Fe(III)}_{0.96}\text{Fe(IV)}_{0.04}\text{O}_{2.64}$
1.00	0.00	0.50	$\text{CaFe(III)O}_{2.50}$

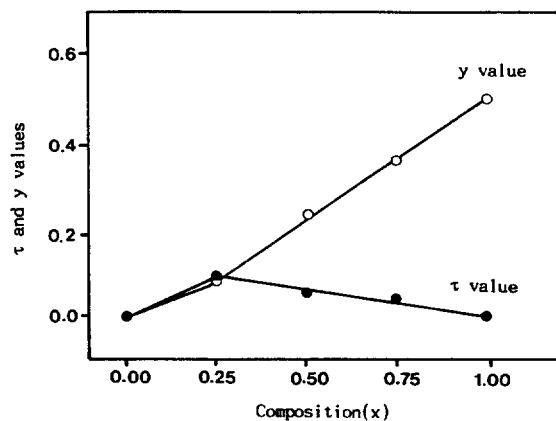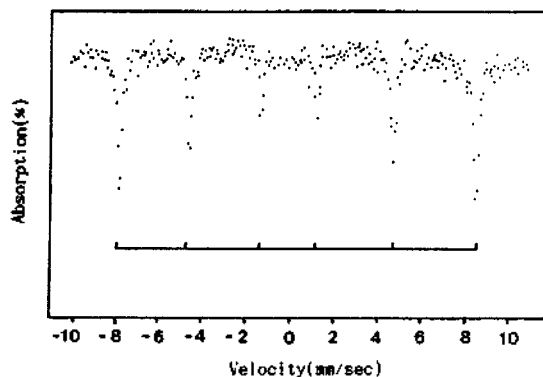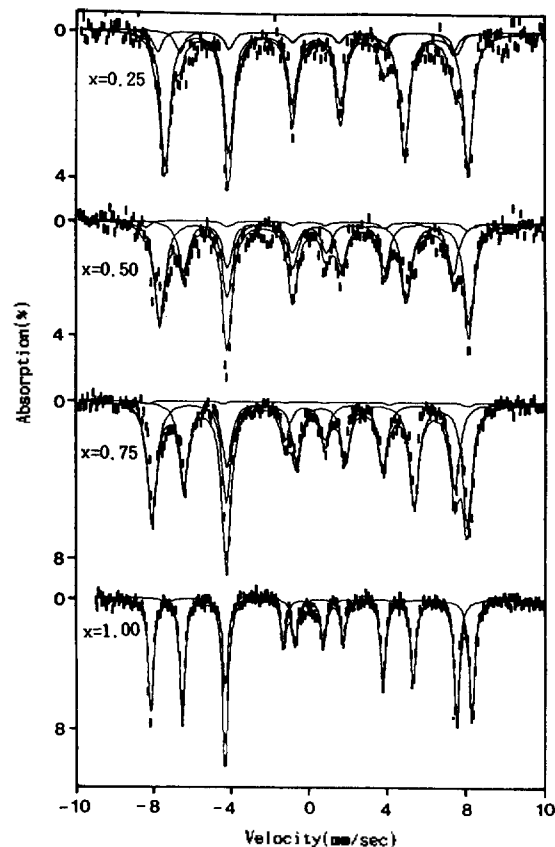**Figure 2.** Plots of  $\tau$  and  $y$  values vs.  $x$  value for the  $\text{Ca}_x\text{Eu}_{1-x}\text{FeO}_{3-y}$  system.**Figure 3.** Mössbauer spectrum of the  $\text{EuFeO}_{3.00}$  system.**Figure 4.** Mössbauer spectra of the compositions of  $x=0.25$ , 0.50, 0.75, and 1.00.**Table 3.** Mössbauer Parameters\* for the  $\text{Ca}_x\text{Eu}_{1-x}\text{FeO}_{3-y}$  System

$x$ value	Ion state	Coordinated site	$\delta$ (mm/sec)	$\Delta E_q$ (mm/sec)	Hn (kOe)
0.00	$\text{Fe}^{3+}$	Oh	0.237	0.121	509
0.25	$\text{Fe}^{3+}$	Oh	0.363	-0.003	485
	$\text{Fe}^{3+}$	Td	0.181	0.474	438
0.50	$\text{Fe}^{4+}$	Oh	-0.074	0.072	480
	$\text{Fe}^{3+}$	Oh	0.338	-0.369	493
	$\text{Fe}^{3+}$	Td	0.180	0.616	431
0.75	$\text{Fe}^{4+}$	Oh	-0.110	0.019	514
	$\text{Fe}^{3+}$	Oh	0.302	-0.561	503
	$\text{Fe}^{3+}$	Td	0.150	0.733	433
1.00	$\text{Fe}^{4+}$	Oh	-0.135	0.046	511
	$\text{Fe}^{3+}$	Oh	0.253	-0.227	513
	$\text{Fe}^{3+}$	Td	0.114	0.377	438

\* $\delta$ : isomer shift,  $\Delta E_q$ : quadrupole splitting, and Hn: hyperfine field.

along [101] strings in every other (010) plane which results in alternating sheets of  $(\text{FeO}_6)$  octahedra and of  $(\text{FeO}_4)$  tetrahedra.

The Mössbauer spectra at room temperature for all the compositions are shown in Figures 3-4. The Mössbauer parameters for all the compositions are listed in Table 3. The spectrum for the composition of  $x=0.00$  or  $\text{EuFeO}_{3.00}$  consists of a series of six lines split under internal magnetic field, which is characteristic of the magnetic ordering below the Néel temperature. The isomer shift, 0.237 mm/sec, and the hyperfine field, 509 KOe, are consistent with Zeeman splitting of  $\text{Fe}^{3+}$  ion at the octahedral site. The large quadrupole splitting, 0.121 mm/sec, reflects the zigzagging form of the octahedral axis along a  $c$ -axis.

The Mössbauer spectra for the compositions of  $x=0.25$ ,

0.50, and 0.75 can be fitted by using three series of sextets as shown in Figure 4. From the result of Mohr salt analysis, it is found out that there exist the mixed valence state between the  $\text{Fe}^{3+}$  and  $\text{Fe}^{4+}$  ions and the high anionic vacancy concentration in each composition. The isomer shift of the first sextet with the largest intensity is consistent with that

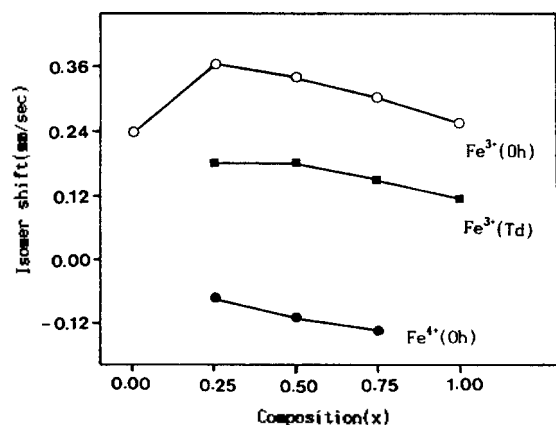


Figure 5. Isomer shift vs.  $x$  value for the  $\text{Ca}_x\text{Eu}_{1-x}\text{FeO}_{3-y}$  system.

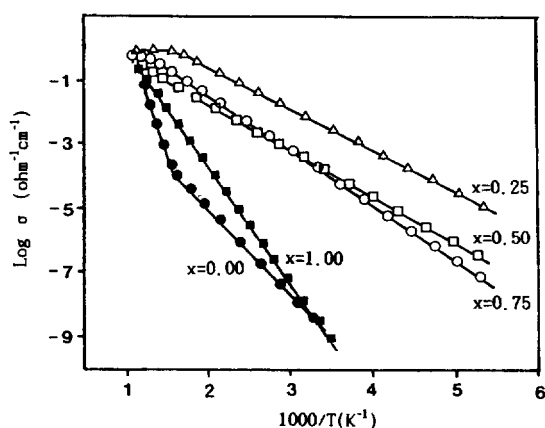


Figure 6. Plots of  $\text{Log } \sigma$  vs.  $1000/T$  for the  $\text{Ca}_x\text{Eu}_{1-x}\text{FeO}_{3-y}$  system.

of  $\text{Fe}^{3+}$  ion at the octahedral site. The intermediate isomer shift of the second sextet, which has the increasing intensity with  $x$  value, allows us to attribute it to the  $\text{Fe}^{3+}$  ion at the tetrahedral site.<sup>7</sup> The negative isomer shift corresponds to that of  $\text{Fe}^{4+}$  ion at the octahedral site. Mössbauer spectrum for the composition of  $x=1.00$  shows two series of six lines with the similar intensity, which is due to the similar concentration of two different  $\text{Fe}^{3+}$  ions located in the octahedral and tetrahedral sites. The isomer shift and hyperfine field of the  $\text{Fe}^{3+}$  ion at the octahedral site are 0.253 mm/sec and 513 KOe, respectively. Those of the  $\text{Fe}^{3+}$  ion at the tetrahedral site are also 0.114 mm/sec and 438 KOe. In fact, such a result might be expected in the brownmillerite-type orthorhombic system.

The plots of the isomer shifts for the differently coordinated Fe ions as a function of  $x$  value are shown in Figure 5. The isomer shifts are in the order of  $\text{Fe}^{3+}(\text{Oh}) > \text{Fe}^{3+}(\text{Td}) > \text{Fe}^{4+}(\text{Oh})$ , which is due to increasing electron density at the nucleus. The isomer shift of  $\text{Fe}^{3+}$  ion at octahedral site is maximum at the composition of  $x=0.25$  and decreases with the increasing  $x$  value. The isomer shifts of  $\text{Fe}^{3+}$  ion at tetrahedral site and  $\text{Fe}^{4+}$  ion at octahedral one decrease with the increasing  $x$  value. It is ascribed to the fact that the  $\text{Fe}^{4+}$  ion with higher charge and smaller ionic radius attracts neighboring oxygen ions and the covalency between

Table 4. Activation Energy of the Electrical Conductivity for the  $\text{Ca}_x\text{Eu}_{1-x}\text{FeO}_{3-y}$  System

$x$ value	Activation energy (eV)
0.00	0.55 (173 K-663 K)
	1.58 (663 K-873 K)
0.25	0.26
0.50	0.29
0.75	0.34
1.00	0.71

the  $\text{Fe}^{4+}$  and oxygen ions becomes significant. Reversely, the  $\text{Fe}^{3+}$  ion neighboring  $\text{Fe}^{4+}$  ion has the decreasing covalency with oxygen ions, which results in increasing isomer shift of  $\text{Fe}^{3+}$  ion. However, since the amount of  $\text{Fe}^{4+}$  ion is maximum at the composition of  $x=0.25$  and decreases in the range of  $0.25 \leq x \leq 0.75$ , the isomer shift of the  $\text{Fe}^{3+}$  ion decreases in the above range. Since the quadrupole splitting results from the electrical field gradient at the nucleus of the iron ion, it reflects asymmetry of coordinating oxygen ligands around the ion. The quadrupole splitting of the iron ion at tetrahedral site is larger than that of octahedral one as shown in Table 3, which is due to a slight shift of the nucleus from oxygen vacancy. The quadrupole splitting of the  $\text{Fe}^{3+}$  ion at octahedral site is abnormally small at the composition of  $x=0.25$ . It reflects the smallest amount of oxygen vacancies with increasing regular arrangement of oxygen ions.

The electrical conductivity measurement has been carried out in the temperature range of 173-873 K under the air pressure as shown in Figure 6. The activation energies of the conductivity are listed in Table 4 for all the compositions in the given temperature ranges. For all the compositions, the conductivity increases with increasing temperature as a semiconductor behavior. The compositions of the  $x=0.00$  and  $x=1.00$  without the  $\text{Fe}^{4+}$  ion has lower conductivity than those of the compositions of  $x=0.25$ , 0.50, and 0.75 with the  $\text{Fe}^{4+}$  ions. The slope change of the Arrhenius plot of conductivity for the composition of  $x=0.00$  occurs at about 663 K. This point is agree with the magnetic ordering one at 662 K reported by Eibschütz.<sup>17</sup> The magnetic ordering temperature for the compositions of  $x=0.25$  to 1.00 is not detected. The composition of  $x=0.25$  has the largest conductivity in the ferrites containing  $\text{Fe}^{4+}$  ion, which is consistent with the maximum amount of  $\text{Fe}^{4+}$  ion in the composition. The activation energy of the conductivity has been varied with an opposite way to the  $\tau$  value as shown in Tables 2 and 4. The mixed valence state between  $\text{Fe}^{3+}$  and  $\text{Fe}^{4+}$  ions leads to high conductivity.

In the study of the  $\text{La}_{1-x}\text{Sr}_x\text{CoO}_{3-y}$  perovskite, Burren *et al.*<sup>18</sup> have suggested that the expression of the Seebeck coefficient in a small polaron hopping model is very suitable for calculating the hole concentration of the system. This suggestion indicates that the hopping model can be also used for other perovskites oxides. As like the similar behavior of the  $\text{La}_{1-x}\text{Sr}_x\text{CoO}_{3-y}$  perovskite in which the conduction depends mainly on the  $\text{Fe}^{4+}$  ion, the conduction mechanism of our system should be represented by the hopping model of the conduction electrons in the mixed valence state be-

tween  $\text{Fe}^{3+}$  and  $\text{Fe}^{4+}$  ions.

**Acknowledgement.** This work was supported by Post-Graduate scholarship from the Dae Woo Foundation in 1993 and also Grant No. 92-25-00-02 from the Korean Science and Engineering Foundation in 1992. Therefore we express our deep appreciation to the authorities concerned.

### References

1. Yo, C. H.; Lee, E. S.; Pyun, M. S. *J. Solid State Chem.* **1988**, *73*, 411.
2. Yo, C. H.; Roh, K. S.; Lee, S. J.; Kim, K. H.; Oh, E. *J. J. Kor. Chem. Soc.* **199**, *35*(3), 211.
3. Ryu, K. H.; Roh, K. S.; Lee, S. J.; Yo, C. H. *J. Solid State Chem.* **1993**, *105*, 550.
4. Rodriguez, J.; Fontcuberta, J.; Longworth, G.; Vallet-Regí M.; González-Calbet, J. M. *J. Solid State Chem.* **1988**, *73*, 57.
5. Buffat, B.; Demazeau, G.; Pouchard, M.; Dance, J. M.; Hagenmuller, P. *J. Solid State Chem.* **1983**, *50*, 30.
6. Parras, M.; Vallet-Regí M.; González-Calbet, J. M.; Allarrio-Franco, M.; Grenier, J. C. *J. Solid State Chem.* **1988**, *74*, 110.
7. Wattiaux, A.; Grenier, J. C.; Pouchard, M.; Hagenmuller, P. *J. Electrochem. Soc.* **1987**, *134*(7), 1714.
8. Lee, S. J., thesis, Ph. D. **1992**.
9. Takano, M.; Kawachi, J.; Nakanishi, J.; Takeda, Y. *J. Solid State Chem.* **1981**, *39*, 75.
10. Racah, P. M.; Goodenough, J. B. *J. Appl. Phys.* **1968**, *39*, 1209.
11. Roosmalen, J. A. M. V.; Cordfunke, E. H. P. *J. Solid State Chem.* **1991**, *93*, 212.
12. Grenier, J. C.; Fournés, L.; Pouchard, M.; Hagenmuller, P. *Mat. Res. Bull.* **1982**, *17*, 55.
13. Gibb, T. C.; Battle, P. D.; Bollen, S. K.; Whitehead, R. *J. J. Mater. Chem.* **1992**, *2*(1), 111.
14. Gibb, T. C. *J. Chem. Soc. Dalton Trans.* **1985**, 1455.
15. Matsuo M.; Gibb, T. C. *J. Solid State Chem.* **1990**, *88*, 485.
16. Takano, M.; Olita, T.; Nakayama, N.; Bando, Y.; Takeda, Y.; Yamamoto, O.; Goodenough, J. B. *J. Solid State Chem.* **1998**, *73*, 140.
17. Eibschütz, M.; Shtrikman, S.; Takeda, Y. *Phys. Rev.* **1967**, *156*(2), 562.
18. Burren, P. R. V.; Dewit, J. H. W. *J. Electrochem. Soc.* **1979**, *126*, 1817.

## Electronic Structure and Properties of High- $T_c$ Substituted YBCO Superconductors: II. MO Calculations on Charged Cluster Models Relating to High- $T_c$ Se-Substituted YBCO Superconductors

Kee Hag Lee\*, Wang Ro Lee, and U-Sung Choi\*\*

Department of Chemistry and

\*\*Department of Electronic Material Engineering, WonKwang University, Iri 570-749, Korea

Received February 7, 19994

Using the extended Hückel molecular orbital method in connection with the tight binding model, we have studied electronic structure and related properties of the charged cluster models relating to superconducting  $\text{YBa}_2\text{Cu}_3\text{O}_{7-x}$  crystals in which O-atoms in regular sites were selectively replaced with Se atoms. In analogy to the isomorphism problem with molecules, we discuss all possible combinations of Se-substitutions in O-sites with one, two, and four Se atoms. The calculations are carried out within charged cluster models for analogues of YBa-copper oxide. Our results suggest that the electronic structure of the symmetrically Se-substituted or Se-added compound is closer to that of the YBCO superconducting compound than that obtained from the unsymmetrical substitution. This applies in particular if O is replaced with Se around the Cu(1) site. Symmetrical substitutions in the  $\text{CuO}_2$  layers give rise to large variations in the electronic structure of  $\text{YBa}_2\text{Cu}_3\text{O}_7$ . This is consistent with the fact that superconductivity is very sensitive to the electronic population of the  $\text{CuO}_2$  layers.

### Introduction

Since the discovery of copper oxide with transition temperature  $T_c$  near 93 K in the Y-Ba-Cu-O systems,<sup>1</sup> a number of attempts have been made to increase  $T_c$  for High- $T_c$  superconductors. These<sup>2-4</sup> and other studies<sup>5-10</sup> have stimulated research to modify the chemical composition by isomorphic replacement of the element in order to raise  $T_c$  and to examine the mechanism of High- $T_c$  superconductivity by sub-

stituting various elements in the  $\text{YBa}_2\text{Cu}_3\text{O}_{7-x}$  compound. It was found that yttrium could be replaced with rare-earth metals<sup>2</sup> with no increase, i.e. enhancement, of critical temperature. Similarly, when barium is replaced with other alkaline earth metals,<sup>3</sup> the overall trend is toward a continuous decrease of  $T_c$ . Also, 3d transition-metal substitution<sup>4</sup> for Cu gives rise to a diminution of  $T_c$  as the doping is increased.

In the  $\text{YBa}_2\text{Cu}_3\text{O}_{7-x}$  system, the superconductive properties are strongly correlated with its oxygen content.<sup>5</sup> Several pa-